

Elastic theory for the vortex-lattice melting in iron-based high- T_c superconductors

Qing-Hu Chen^{1,2}, Qing-Miao Nie³, Jian-Ping Lv^{1,2}, Tin-Cheung Au Yeung^{1,4}

¹ Center for Statistical and Theoretical Condensed Matter Physics, Zhejiang Normal University, Jinhua 321004, P. R. China

² Department of Physics, Zhejiang University, Hangzhou 310027, P. R. China

³ Department of Applied Physics, Zhejiang University of Technology, Hangzhou 310023, China

⁴ School of Electric and Electronic Engineering, Nanyang Technological University, Singapore 639798

E-mail: qhchen@zju.edu.cn

Abstract. The vortex-lattice melting transitions in two typical iron-based high- T_c superconductor $Ba(Fe_{1-x}Co_x)_2As_2$ (122-type) and $Nd(O_{1-x}F_x)FeAs$ (1111-type) for magnetic fields both parallel and perpendicular to the anisotropy axis are studied within the elastic theory. Using the parameters from experiments, the vortex-lattice melting lines in the H-T diagram are located systematically by various groups of Lindemann numbers. It is observed that the theoretical results for the vortex melting on both $Ba(Fe_{1-x}Co_x)_2As_2$ and $Nd(O_{1-x}F_x)FeAs$ for parallel fields agree well with the recent experimental data. The future experimental results for the vortex melting can be compared with the present theoretical prediction by tuning reasonable Lindemann numbers.

1. Introduction

Recently, the newly discovered iron-based superconductors have attracted considerable scientific interest both experimentally [1, 2, 3, 4, 5, 6, 7, 8, 9, 10, 11, 12, 13, 14, 15, 16, 17] and theoretically [18, 19, 20, 21, 22, 23]. First, the novel superconductivity in 1111 phase $FeAs$ superconductors was reported experimentally, giving a new path to high temperature superconductivity. The $LaOFeAs$ under doping with F^- ions at the O^{2-} sites was found to exhibit superconductivity with $T_c = 26K$ [1], and the superconductivity was also observed with holes doping [2]. Then T_c was surprisingly increased up to above 40K when La in $LaO_{1-x}F_xFeAs$ was substituted by other rare earth elements [3, 4]. It was quickly observed later that T_c is about 55K in $SmO_{1-x}F_xFeAs$ [5, 6] and $Gd_{1-x}Th_xOFeAs$ [7]. It is a first non-copper-based superconductors in which the maximum critical temperature is much higher than the theoretical value predicted from BCS theory [24]. On the other hand, the 122 phase iron-based superconductor $BaFe_2As_2$ was discovered more recently [8], and the superconducting critical temperature was found to be as high as 38K by hole-doping. It is observed that the electron doping of which by Co [9] and Ni [10] also induce superconductivity. Although there are some theoretical studies on iron-based superconductors, the type-II superconductivity as well as the mechanism of superconductivity are not well understood to date.

The vortex-lattice solid (glass with random pinning) state with zero linear resistivity is crucial for the application of high- T_c superconductors, thus the melting of vortex-lattice in bulk type-II superconductors is of great significance [25, 26, 27, 28, 29]. The main aspect of Lindemann criterion suggests that the lattice melts when the root mean square thermal displacements of the components of a lattice reach a certain fraction of the equilibrium lattice spacing, such a criterion was first adopted to study the vortex-lattice melting transition in type-II superconductors with a magnetic field parallel to the anisotropic axis, then this approach was used to draw the melting lines in the case of magnetic field perpendicular to the anisotropic axis [30, 31, 32, 33]. Since the upper critical field is also high [13, 12] in iron-based high- T_c superconductors, the thermal fluctuation may drive the vortex-lattice to a vortex liquid in a field far below the upper critical field [30] through vortex melting. We will extend the elastic theory to study the vortex melting in these newly discovered superconductors.

In this paper, using the parameters measured in recent experiments, we study the vortex-lattice melting transitions for two typical iron-based layered superconductors $Ba(Fe_{1-x}Co_x)_2As_2$ (122-type) with low anisotropy [9, 12] and $Nd(O_{1-x}F_x)FeAs$ (1111-type) with high anisotropy [4, 13], in the framework of the elastic theory. The melting lines for magnetic fields both parallel and perpendicular to the anisotropic axis are systematically located with different groups of Lindemann numbers. A comparison with current experimental findings is made. The present paper is organized as follows. In Section 2, we introduce the theoretical method used in this work, Section 3 presents the main results, finally, we give a short summary.

2. Elastic theory

We will consider the field B both parallel and perpendicular to the anisotropy axis (i.e. c-axis in this paper), the elastic theories in both cases are presented respectively.

2.1. Thermal fluctuations

Whether the field is parallel or perpendicular to c-axis, for ideal triangular vortex-line lattice, the free energy in elastic theory can be expressed in an unified way with quadratic terms of the deviation vector $\mathbf{u} = (u_x, u_y)$ describing the fluctuations of vortices from their equilibrium positions[25, 26, 30, 31, 32, 33]

$$F = \frac{1}{2} \int \frac{d^3\mathbf{k}}{(2\pi)^3} \mathbf{u} \cdot \mathbf{C} \cdot \mathbf{u}, \quad (1)$$

The matrix $\mathbf{C}$ for fields parallel to the c-axis is different from that for fields perpendicular to it. We denote $\mathbf{C}^c$ and $\mathbf{C}^{ab}$ to be the elastic matrix for the fields parallel and perpendicular to c-axis, respectively, which are given as follows

$$\mathbf{C}^c = \begin{pmatrix} c_L k_x^2 + c_{66} k_\perp^2 + c_{44} k_z^2 & c_L k_x k_y \\ c_L k_x k_y & c_L k_y^2 + c_{66} k_\perp^2 + c_{44} k_z^2 \end{pmatrix} \quad (2)$$

and

$$\mathbf{C}^{ab} = \begin{pmatrix} c_{11} k_x^2 + c_{66}^h k_y^2 + c_{44}^h k_z^2 & c_{11} k_x k_y \\ c_{11} k_x k_y & c_{66}^e k_x^2 + c_{11} k_y^2 + c_{44}^e k_z^2 \end{pmatrix} \quad (3)$$

In matrix $\mathbf{C}^c$, $k_\perp^2 = k_x^2 + k_y^2$, c_{66} , c_L , and c_{44} are the wave-vector-dependent shear, bulk, and tilt elastic moduli[26, 34, 35], respectively, which are determined as follows

$$c_{44}(\mathbf{k}) = \frac{B^2}{4\pi} \left[\frac{M}{M_z} \right] \frac{1-b}{2b\kappa^2} \left[\frac{1}{k_\perp^2 + (M/M_z)(k_z^2 + m_\lambda^2)} + 1 \right] \quad (4)$$

and

$$c_{11}(\mathbf{k}) = \frac{B^2}{4\pi} \frac{1-b}{2b\kappa^2} \left[\frac{k^2 + (M/M_z)m_\lambda^2}{(k^2 + m_\lambda^2)[k_\perp^2 + (M/M_z)(k_z^2 + m_\lambda^2)]} - \frac{1}{k_\perp^2 + (M/M_z)k_z^2 + m_\xi^2} \right] \quad (5)$$

Where we have defined $m_\lambda^2 = \frac{1-b}{2b\kappa^2}$ and $m_\xi^2 = \frac{1-b}{b}$, M is a quasi-particle effective mass in xy -plane, M_z describes along c-axis, $b = B/B_{c2}$ with B_{c2} is the upper critical field, and $\kappa = \lambda_\perp/k_\perp$. The bulk modulus is $c_L = c_{11} - c_{66}$ with shear modulus

$$c_{66} = \frac{B_{c2}^2}{4\pi} \frac{b(1-b)^2}{8\kappa^2}. \quad (6)$$

The matrix $\mathbf{C}^{ab}$ also contains some elastic moduli. Since the anisotropy exists here, tilt and shear modulus are not isotropic any more. For example, $c_{44}^h(\mathbf{k})$ ($c_{44}^e(\mathbf{k})$) is tilt modulus along (perpendicular to) c-axis. Similarly, c_{66}^h (c_{66}^e) represents shear modulus

parallel to (perpendicular to) the anisotropy axis c . For the detailed expressions for elastic moduli, one may refer to Ref. [33]

The thermal fluctuations of the vortices are given by inverting the kernel $\mathbf{C}(\mathbf{k})$ as follows

$$\langle u_\alpha^2 \rangle = \frac{k_B T}{(2\pi)^3} \int d\mathbf{k} [\mathbf{C}_{\alpha\alpha}^\beta]^{-1}(\mathbf{k}), \alpha = x, y, \beta = c, ab \quad (7)$$

The integrations in Eq. (7) are over $0 < k_z < \infty$ and within the first Brillouin zone (BZ) for k_x and k_y . To be specific, we consider a lattice structure as the low temperature equilibrium state as shown in Fig. 1 of Ref. [33], where the lattice spacings are $a_x = a$ and $a_y = a\sqrt{3}/2$ for fields parallel to c -axis, $a_x = a/\sqrt{\gamma}$ with $\hat{x} \parallel \hat{c}$ and $a_y = a\sqrt{3\gamma}/2$ for fields perpendicular to c -axis with $\gamma^2 = m_c/m_{ab}$ and $a = \sqrt{2\Phi_0/\sqrt{3}B}$.

For parallel fields, we consider the mean-square displacement of a vortex lattice from the equilibrium $d^2(T) = u_x^2 + u_y^2$ which can be written as

$$d^2(T) = \frac{k_B T}{(2\pi)^3} \int d\mathbf{k} \left[\frac{1}{c_{66}k_\perp^2 + c_{44}k_z^2} + \frac{1}{c_{11}k_\perp^2 + c_{44}k_z^2} \right] \quad (8)$$

For convenience, we introduce the dimensionless wave vector $\mathbf{q} = (k_x/\Lambda_x, k_y/\Lambda_y, k_z/\Lambda)$, where $\Lambda_{x,y}$ are the wave numbers at the edges of the first BZ. Explicitly, they are given as $\Lambda_x = 4\pi/3a$ and $\Lambda_y = 2\pi/a\sqrt{3}$ for fields parallel to c -axis and $\Lambda_x = 4\pi\sqrt{\gamma}/3a$ and $\Lambda_y = 2\pi/a\sqrt{3\gamma}$ for fields perpendicular to c -axis. The unit of wave number in k_z direction is taken as $\Lambda = \sqrt{4\pi B/\Phi_0} = \sqrt{8\pi/\sqrt{3}a^2}$. The thermal fluctuations are then expressed as

$$d^2(T) = \frac{\Lambda}{B^2} \frac{k_B T}{(2\pi)^3} \int d\mathbf{q} \tilde{C}_{\alpha\alpha}^{-1}(\mathbf{q}) \equiv \frac{\Lambda}{B^2} \frac{k_B T}{(2\pi)^3} I_{dd}, \quad \text{for } B \parallel c \quad (9)$$

and

$$\langle u_\alpha^2 \rangle = \frac{\Lambda}{B^2} \frac{k_B T}{(2\pi)^3} \int d\mathbf{q} \tilde{C}_{\alpha\alpha}^{-1}(\mathbf{q}) \equiv \frac{\Lambda}{B^2} \frac{k_B T}{(2\pi)^3} I_{\alpha\alpha}, \quad \alpha = x, y, \text{ for } B \perp c \quad (10)$$

with the normalized matrix $\tilde{\mathbf{C}}(\mathbf{q}) \equiv \mathbf{C}(\mathbf{q})/B^2\Lambda_x\Lambda_y$.

2.2. Lindemann criterion

The Lindemann criterion presumes that the lattice melts, when the root mean square thermal displacements of the components of a lattice reach some fraction of the equilibrium lattice spacing. For two cases, we write the usual isotropic Lindemann criterion for parallel fields,

$$\langle d^2 \rangle = c^2 a^2. \quad (11)$$

and the anisotropic one for perpendicular fields,

$$\langle u_x^2 \rangle = c_x^2 a_x^2, \quad \langle u_y^2 \rangle = c_y^2 a_y^2. \quad (12)$$

with c_x and c_y are two Lindemann numbers for two transverse directions. Combining the Lindemann criterion and the elastic theory, we can get the melting equations for two cases,

$$\frac{t}{\sqrt{1-t}} = c^2 \frac{32\pi^4 \kappa^2}{\sqrt{3\varepsilon_d}} \frac{\sqrt{b}}{I_{dd}}, \quad \text{for } B \parallel c \quad (13)$$

and

$$\frac{t_\alpha}{\sqrt{1-t_\alpha}} = \left(\frac{a_\alpha}{a}\right)^2 c_\alpha^2 \frac{32\pi^4 \kappa^2}{\sqrt{3\varepsilon}} \frac{\sqrt{b_\alpha}}{I_{\alpha\alpha}}, \quad \alpha = x, y, \text{ for } B \perp c \quad (14)$$

with ε the Ginzburg parameter $\varepsilon_d = 16\pi^3 \kappa^4 (k_B T_c)^2 / \Phi_0^3 H_{c2}^c(0)$ and $\varepsilon = 16\pi^3 \kappa^4 (k_B T_c)^2 / \Phi_0^3 H_{c2}^{ab}(0)$.

2.3. Layer pinning effect

When fields perpendicular to c-axis, the effect of layer pinning reduces fluctuations in both directions and induces an additional momentum-independent term to the elastic matrix in Eq. (3) such that

$$\mathbf{C}_{\text{lp}}^{\text{ab}} = \begin{pmatrix} c_{11}k_x^2 + c_{66}^h k_y^2 + c_{44}^h k_z^2 + \Theta & c_{11}k_x k_y \\ c_{11}k_x k_y & c_{11}k_y^2 + c_{66}^e k_x^2 + c_{44}^e k_z^2 \end{pmatrix}, \quad (15)$$

where

$$\frac{\Theta}{\Lambda^2 B^2} = \frac{4\sqrt{\pi}}{\beta_A \kappa^2 \gamma} \left(\frac{\xi_c^0}{s}\right)^3 \frac{1-b}{b^2} \frac{1}{(1-t)^{3/2}} e^{-\frac{8}{1-t} \left(\frac{\xi_c^0}{s}\right)^2} \quad (16)$$

is proportional to the critical depinning current [36], with $\xi_c^0 \equiv \xi_c(T=0)$, $\beta_A \approx 1.16$ and s the layer separation.

3. Results

3.1. Vortex melting in $Ba(Fe_{1-x}Co_x)_2As_2$.

We study the vortex melting in $Ba(Fe_{1-x}Co_x)_2As_2$ ($x=0.1$) as a representative of 122-type iron-based superconductors[11]. The parameter measured from a most recent experiment [12] gives $T_c = 22\text{K}$, $\lambda_\perp = 160\text{nm}$, $\xi_\perp = 2.44\text{nm}$, $H_{c2}^c(T=0) = 50\text{T}$, $H_{c2}^{ab}(T=0) = 70\text{T}$, and $s = 23\text{\AA}$. The anisotropic parameter γ falls from 2.0 to 1.5 with the decrease of temperature. In our calculation, we observe that the melting lines determined in the framework of elastic theory only change slightly with the variation of γ (in the range of 1.5 $\sim$ 2.0). So we set $\gamma = 2$ in our calculations.

We first calculate the melting line for the parallel fields with various Lindemann numbers. It is interesting to note in Fig. 1 that the vortex melting line for $Ba(Fe_{1-x}Co_x)_2As_2$ obtained in this paper is well consistent with the irreversible line measured experimentally [12] with Lindemann number $c = 0.2$. The irreversibility line in superconductor is usually regarded as the melting line. [30]

Then we study the vortex melting for perpendicular fields. Due to the lacking of the experimental data until now, three groups of Lindemann numbers are selected to

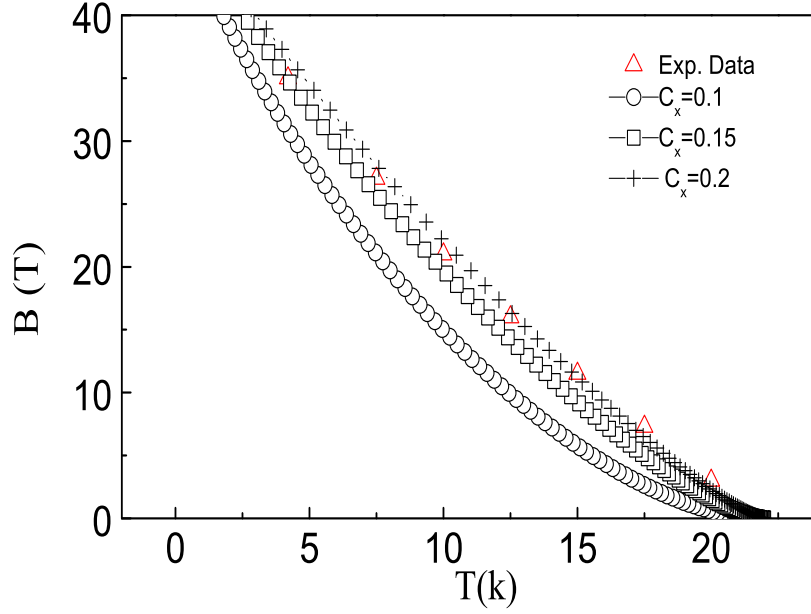


Figure 1. Comparison of vortex-lattice melting lines for $Ba(Fe_{1-x}Co_x)_2As_2$ with experimental results in Ref. [12] for magnetic fields parallel to c -axis.

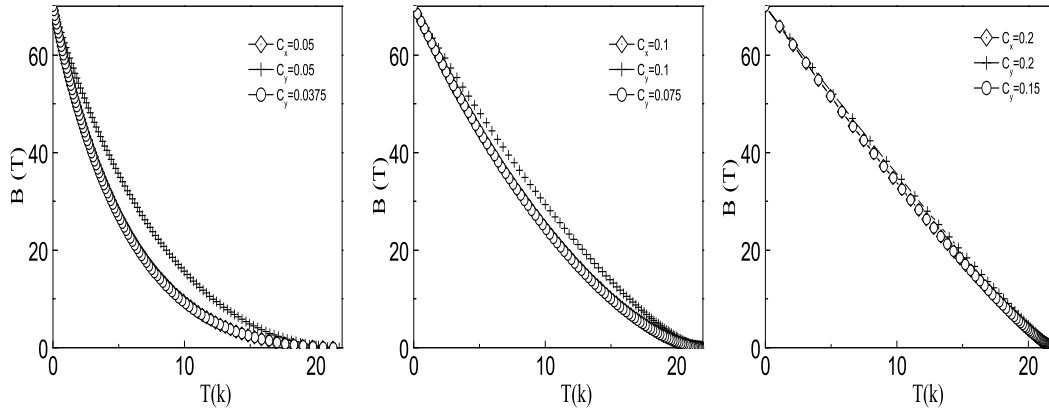


Figure 2. Vortex-lattice melting lines for $Ba(Fe_{1-x}Co_x)_2As_2$ with magnetic field perpendicular to c -axis (without intrinsic layer pinning). From left to right, $C_x = 0.05, C_y = 0.05, C_y = 0.0375$; $C_x = 0.1, C_y = 0.1, C_y = 0.075$; $C_x = 0.2, C_y = 0.2, C_y = 0.15$.

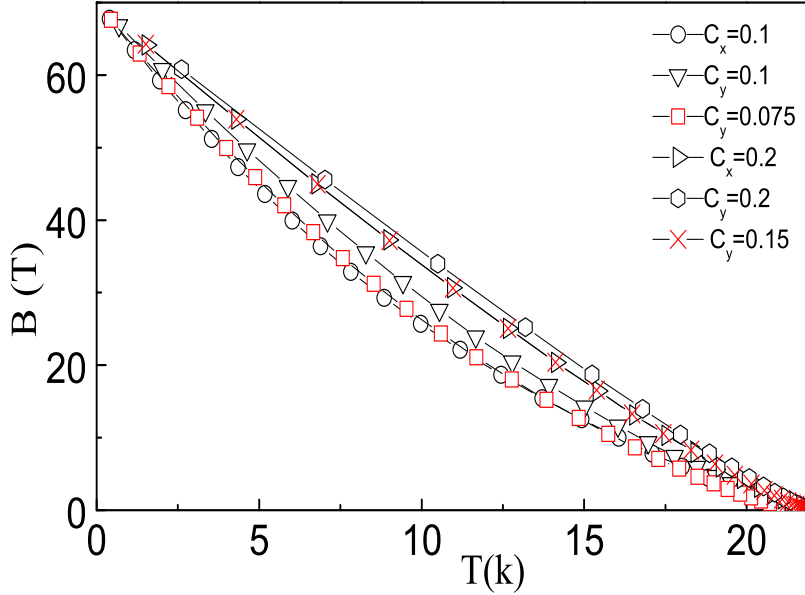


Figure 3. Vortex-lattice melting lines for $Ba(Fe_{1-x}Co_x)_2As_2$ with magnetic field perpendicular to c-axis (with intrinsic layer pinning).

calculate the melting lines ($C_x = 0.05, C_y = 0.05, C_y = 0.0375$; $C_x = 0.1, C_y = 0.1, C_y = 0.075$; $C_x = 0.2, C_y = 0.2, C_y = 0.15$). The obtained melting curves are shown in Fig. 2. The future experimental results can be inserted into this figure, and be compared with interpolation values obtained here.

Setting $C_x = C_y$, we obtain two curves as shown in Figs. 2(a-c), as in Ref. [31]. As pointed out in Ref. [32], to interpret these two curves as two "melting lines" and thus reach to a conclusion of an intermediate phase is unphysical, since the elastic theory can give at best one melting line. To impose the same Lindemann number along the two directions is of no physical basis. In order to achieve a single melting line, one can tune the Lindemann numbers in the two directions. A good collapse of the melting lines in two directions can be achieved if setting the ratio $c_x/c_y \approx 1.33$. It is interesting to note that this ratio is very close to 1.37 observed in Ref. [33] using parameters of cuprate superconductors.

The vortex melting for fields perpendicular to the c-axis is also influenced by the layer pinning. In order to study this intrinsic layer pinning effect, the matrix (15) is used to calculate the thermal fluctuations along two transverse directions. The melting lines for two groups of Lindemann number ($C_x = 0.1, C_y = 0.1, C_y = 0.075$; $C_x = 0.2, C_y = 0.2, C_y = 0.15$) are collected in Fig. 3. A good collapse can also be obtained by setting the same ration $c_x/c_y \approx 1.33$. The future experimental data can be also compared with these values.

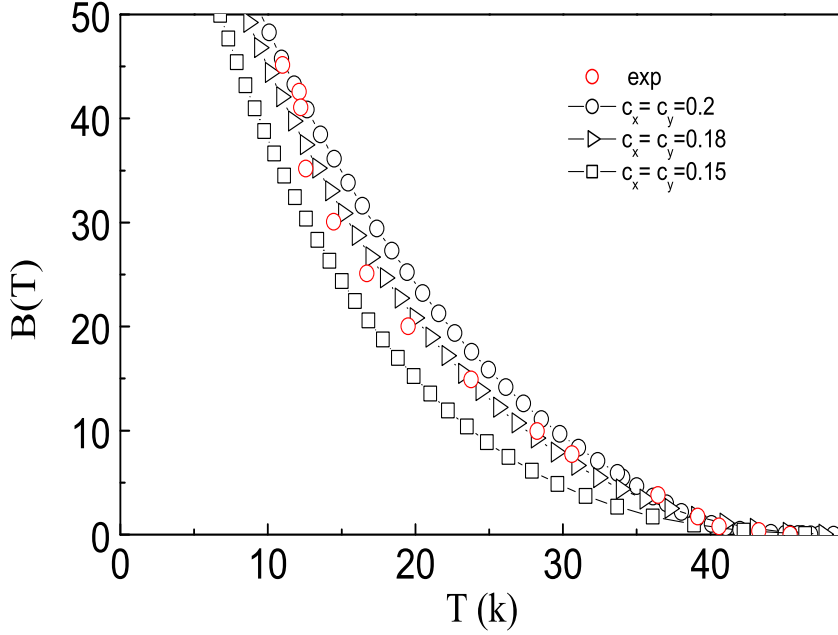


Figure 4. Vortex-lattice melting lines for $Nd(O_{1-x}F_x)FeAs$ with magnetic field parallel to c-axis.

3.2. Vortex melting in $Nd(O_{1-x}F_x)FeAs$.

We now turn to another typical iron-based layered superconductor $Nd(O_{1-x}F_x)FeAs$ (1111-type) [13, 14, 15, 16]. We take parameters from [15], $T_c = 49K$, $\lambda_{\perp} = 200nm$, $\xi_{\perp} = 2.3nm$, $H_{c2}^c(T = 0) = 95T$, $H_{c2}^{ab}(T = 0) = 220T$, $\gamma^2 = 25$. The separation between the FeAs planes is given by twice of the lattice parameter $s = 2c \approx 17\text{\AA}$ [1, 14, 22].

Similarly, we first calculate the melting lines for the fields parallel to c-axis, as shown in Fig. 4. Since the melting line has not been explicitly reported, the data at which the resistance reaches the small percentage (0.5%) of the normal-state resistance in Ref. [15] is regarded the approximated melting one here, which is also collected in Fig. 4. Interestingly, the theoretical melting line with $c = 0.18$ is consistent with the experimental data in a considerable wide temperature range. The discrepancy between experiment and theory becomes larger at high magnetic fields and low temperatures. A trend of temperature independent melting data is shown at high magnetic fields in experiments, implying that the dimensional crossover occurs at this regime. If the vortex system is of two dimensional nature at high magnetic fields, the melting line is almost independent of the temperature[30],

Next, We calculate the melting lines when the fields perpendicular to c-axis, which are shown in Fig. 5. For perpendicular fields, three different groups of Linderman numbers ($C_x = 0.1, C_y = 0.1, C_y = 0.075$; $C_x = 0.2, C_y = 0.2, C_y = 0.15$; $C_x = 0.3, C_y =$

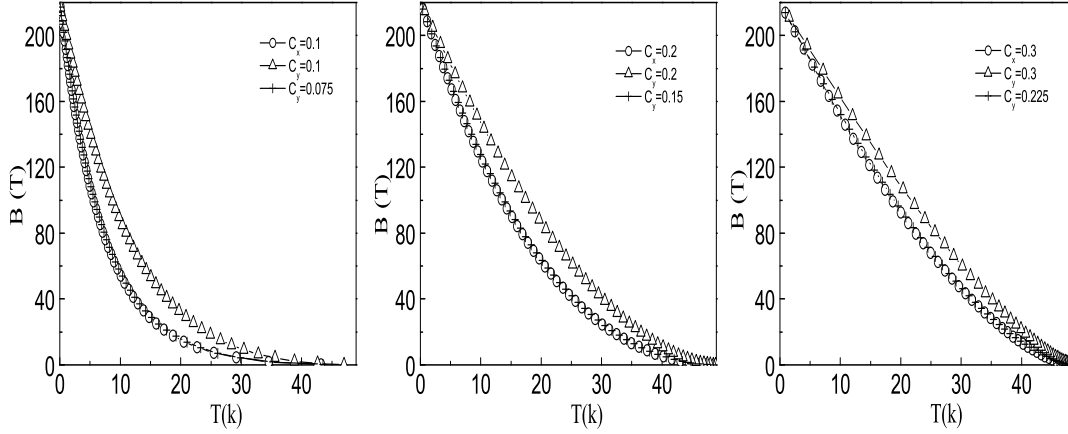


Figure 5. Vortex-lattice melting lines for $Nd(O_{1-x}F_x)FeAs$ with magnetic field perpendicular to c -axis (without intrinsic layer pinning). From left to right, $C_x = 0.1, C_y = 0.1, C_y = 0.075$; $C_x = 0.2, C_y = 0.2, C_y = 0.15$; $C_x = 0.3, C_y = 0.3, C_y = 0.225$.

0.3, $C_y = 0.225$) are used to locate the melting lines. A good collapse of the melting lines in two directions can be also achieved if setting the ratio $c_x/c_y \approx 1.33$, nearly the same as that in 122 type.

We also investigate the intrinsic layer pinning effect on the vortex melting in $Nd(O_{1-x}F_x)FeAs$ sample. The results are exhibited in Fig. 6. Surprisingly, we observe an intersection between two melting lines with two transverse directions for typical Lindemann numbers, which is not shown in the above 122 type. Obviously, a collapse of these two curves could not be achieved by setting any ration c_x/c_y . It is implied that the intermediate smectic phase [31, 32, 33] may exist in $Nd(O_{1-x}F_x)FeAs$. However, its identification is beyond the phenomenological Lindemann theory. It is interesting to note that, when the exponentially weak intrinsic pinning was taken into account for a weakly anisotropic $Ba(Fe_{1-x}Co_x)_2As_2$, the vortex melting behavior is only changed slightly, but for the strongly anisotropic $Nd(O_{1-x}F_x)FeAs$, the intrinsic pinning would play a much more significant role.

4. Summary

In terms of the elastic theory, we have studied the thermal fluctuations in two typical iron-based superconductors $Ba(Fe_{1-x}Co_x)_2As_2$ and $Nd(O_{1-x}F_x)FeAs$ for magnetic fields parallel and perpendicular to the anisotropy axis. Using the parameters of these superconductors from experiments, the melting lines with various Lindemann numbers are composed. Interestingly, we can derive the melting line observed in

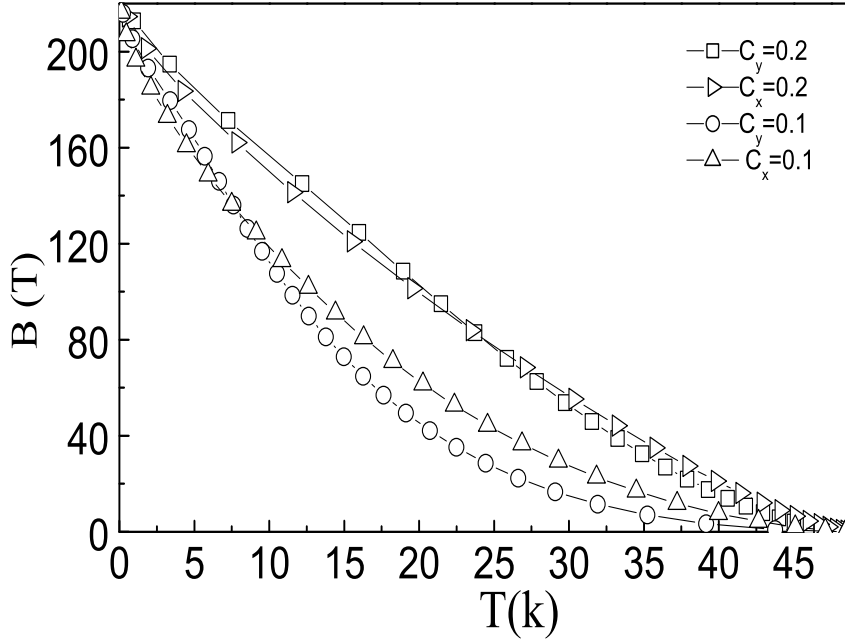


Figure 6. Vortex-lattice melting lines for $Nd(O_{1-x}F_x)FeAs$ with magnetic field perpendicular to c -axis (with intrinsic layer pinning).

both $Ba(Fe_{1-x}Co_x)_2As_2$ [12] and $Nd(O_{1-x}F_x)FeAs$ [15] for magnetic field parallel to the c -axis. Neglecting the layer pinning effect, it is found that thermal fluctuations normalized by vortex separations in the two transverse directions for parallel field are proportional to each other, similar to those observed in cuprate superconductors[32, 33]. Interestingly, the intrinsic layer pinning play much more important role on the vortex melting in $Nd(O_{1-x}F_x)FeAs$ than in $Ba(Fe_{1-x}Co_x)_2As_2$. More experimental works are motivated to confirm our prediction by comparing the melting data with the interpolation one presented here. The present prediction may in turn provide a guide or reference to locate the melting line in future experiments.

5. Acknowledgements

This work was supported by National Natural Science Foundation of China under Grant Nos. 10774128(QHC) and 10804098(QMN), PCSIRT (Grant No. IRT0754) in University in China, National Basic Research Program of China (Grant Nos. 2006CB601003 and 2009CB929104), Zhejiang Provincial Natural Science Foundation under Grant No. Z7080203, and Program for Innovative Research Team in Zhejiang Normal University,

References

- [1] Y Kamihara, T Watanabe, M Hirano and H Hosono 2008 *J. Am. Chem. Soc.* **130** 3296
- [2] H H Wen, G Mu, L Fang, H Yang and X Y Zhu 2008 *Europhys. Lett.* **82** 17009
- [3] X H Chen, T Wu, G Wu, R H Liu, H Chen and D F Fang 2008 *Nature(London)* **453** 761
- [4] Z A Ren, J Yang, W Lu, W Yi, X L Shen, Z C Li, G C Che, X L Dong, L L Sun, F Zhou and Z X Zhao 2008 *Europhys. Lett.* **82** 57002
- [5] Z A Ren, W Lu, J Yang, W Yi, X L Shen, Z C Li, G C Che, X L Dong, L L Sun, F Zhou and Z X Zhao 2008 *Chin. Phys. Lett.* **25** 2215
- [6] R H Liu, G Wu, T Wu, D F Fang, H Chen, S Y Li, K Liu, Y L Xie, X F Wang, R L Yang, C He, D L Feng and X H Chen 2008 *Phys. Rev. Lett.* **101** 087001
- [7] C Wang, L J Li, S Chi, Z W Zhu, Z Ren, Y K Li, Y T Wa, X Lin, Y G Luo, X F Xu, G H Cao and Z A Xu 2008 *Europhys. Lett.* **83** 67006
- [8] M Rotter, M Tegal and D Johrendt 2008 *Phys. Rev. Lett.* **101** 107006
- [9] A S Sefat, M A McFuire, B C Sales, R Jin, J Y Howe and D Mandrus 2008 *Phys. Rev. Lett.* **101** 117004
- [10] L J Li, Q B Wang, Y K Luo, H Chen, Q Tao, Y K Li, X Lin, M He, Z W Zhu, G H Cao and Z A Xu 2009 *New J. Phys.* (in press)
- [11] H Q Yuan, J Singleton, F F Balakirev, G F Chen, J L Luo, N L Wang, 2009 *Nature(London)* **457** 565
- [12] A Yamamoto, J Jaroszynski, C Tarantini, L Balicas, J Jiang, A Gurevich, D C Larbalestier, R Jin, A S Sefat, M A McGuire, B C Sales, D K Christen and D Mandrus 2008 arXiv:0810.0699
- [13] U Welp, R Xie, A E Koshelev, W K Kwok, P Cheng, L Fang and H H Wen 2008 arXiv:0807.4196
- [14] Y Jia, P Cheng, L Fang, H Q Luo, H Yang, C Ren, L Shan, C Z Gu, H H Wen 2008 *Appl. Phys. Lett.* **93** 032503
- [15] J Jaroszynski, F Hunte, L Balicas, Y J Jo, I Raicevic, A Gurevich, D C Larbalestier F F Balakirev, L Fang, P Cheng, Y Jia, and H H Wen, 2008 *Phys. Rev. B* **78** 174523
- [16] R Khasanov, H Luetkens, A Amato, H Klauss, Z A Ren, J Yang, W Lu and Z X Zhao 2008 *Phys. Rev. B* **78** 092506
- [17] Y Yin, M Zech, T L Williams, X F Wang, G Wu, X H Chen, J E Hoffman 2008 arXiv:0810.1048
- [18] I I Mazin, D J Singh, M D Johannes, and M H Du 2008 *Phys. Rev. Lett.* **101** 057003
- [19] Q Si and E Abrahams 2008 *Phys. Rev. Lett.* **101** 076401
- [20] F J Ma, Z Y Lu, and T Xiang 2008 *Phys. Rev. B* **78**, 224517 and 2008 arXiv:0806.3526
- [21] C Fang, H Yao, W F Tsai, J P Hu, and S A Kivelson, 2008 *Phys. Rev. B* **77** 224509
- [22] J P Lv and Q H Chen 2008 *Phys. Rev. B* **78** 144507
- [23] G M Zhang, Y H Su, Z Y Lu, Z Y Weng, D H Lee, T Xiang, 2008 arXiv:0809.3874
- [24] W L McMillan, 1968 *Phys. Rev.* **167** 331
- [25] E H Brandt 1989 *Phys. Rev. Lett.* **63** 1106
- [26] A Houghton, R A Pelcovits and A Sudbo 1989 *Phys. Rev. B* **40** 6763
- [27] H Safar, P L Gammel, D A Huse, D J Bishop, J P Rice and D M Ginsberg 1992 *Phys. Rev. Lett.* **69** 824
- [28] R Cubitt, E M Forgan, G Yang, S L Lee, D Mck Paul, H A Mool, M yethiraj, P H Kes, T W Li, A A Menovsky, Z Tarnawski and K Mortensen 1993 *Nature(London)* **365** 407
- [29] I F Herbut and Z Tesanovic, 1994 *Phys. Rev. Lett.* **73** 484
- [30] G Blatter, M V Feigel'man, V B Geshkenbein, V B Larkin and V M Vinokur 1994 *Rev. Mod. Phys.* **66** 1125
- [31] E W Carlson, A H Castro Neto, and D K Campbell 2003 *Phys. Rev. Lett.* **92** 087001
- [32] X Hu and Q H Chen 2004 *Phys. Rev. Lett.* **92** 209701
- [33] Q M Nie, M B Luo, Q H Chen and X Hu 2005 *Europhys. Lett.* **71** 445
- [34] E H Brandt, 1977 *J. Low. Temp. Phys.* **26** 709
- [35] L J Campbell, M M Doria and V G Kogan 1988 *Phys. Rev. B* **38** 2439

- [36] B I Ivlev and N B Kopnin 1990 J. Low Temp Phys. **80** 161; 1990 J. Low Temp Phys. **80** 187